

## Hybrid Inorganic/Organic Diblock Copolymers. Nanostructure in Polyhedral Oligomeric Silsesquioxane Polynorbornenes.

Timothy S. Haddad\*, Patrick T. Mather§, Hong G. Jeon‡, Seung B. Chun§, Shawn H. Phillips†

\*ERC Corp., and †Air Force Research Lab, Edwards Air Force Base, CA 93524

§Institute of Materials Science, University of Connecticut, CT 06269

‡Systran Corp., Air Force Research Lab, Wright Patterson Air Force Base, OH 45433

### ABSTRACT

Our main approach to the synthesis and study of hybrid organic/inorganic materials involves incorporating nano-size inorganic polyhedral oligomeric silsesquioxane (POSS) clusters into various polymeric resins. A typical POSS cluster is a discrete silicon and oxygen framework solubilized with organic groups and contains a single reactive site. This lone site of reactivity is used to covalently attach the inorganic macromers pendent to a polymer backbone without causing any crosslinking. This strategy permits the synthesis of melt processable, linear hybrid polymers containing pendent inorganic clusters, and allows us to study the effect these clusters have on chain motion, polymer properties and morphology. The synthesis of norbornenyl-based (POSS) macromers, their ring opening metathesis copolymerizations with varying amounts of norbornene, and analysis of the effect of the pendent POSS group is presented. Ring opening metathesis polymerization permits the easy synthesis of both random and diblock copolymers. Transmission electron microscopy (TEM) clearly images POSS-rich domains against the POSS-free regions. Major differences in polymer morphology are observed as the amount of inorganic POSS is varied, between random and diblock copolymers, as well as between polymers that differ only in the solubilizing cycloalkyl groups on the POSS cluster.

### INTRODUCTION

The design of new materials with enhanced properties continues to be a driver for the investigation of hybrid materials. As hybrid materials are copolymers based on inorganic and organic comonomers, they display enhanced properties by bridging the property space between two dissimilar types of materials [1]. A typical hybrid material will contain a crosslinked inorganic phase bound (often covalently) with an organic phase. An alternative approach, that several groups have pursued, is to append well-defined monodisperse silica-like clusters into thermoplastic resins [2-7]. The resulting hybrid polymers are easily processed, yet their physical properties are modified by the effect of the nano-sized inorganic component.

Our research has focused on using well-defined POSS (polyhedral oligomeric silsesquioxane) molecules for the inorganic component. Thermoplastics modified with POSS tend to show an increase in glass transition and modulus, a large increase in heat distortion temperature and a reduction in flammability. Changes to the rheological properties appear to

derive from interaction between POSS groups themselves or with the polymer backbone. Characteristic polymer relaxation times are increased and we have found evidence for retardation of chain motion. Interestingly, the alkyl groups on the POSS cage play a major role in defining the overall effect of the POSS cage (See Figure 1 for a picture of a POSS). The subtle change from cyclohexyl to cyclopentyl groups at the POSS cage renders major differences to the material properties of the hybrid polymer [2].

Recently, we found that TEM images of polynorbornenes containing POSS-norbornenyl groups *randomly* distributed throughout the polymer show phase separation on very short length scales and no long range order [8]. We have now synthesized diblock norbornenyl copolymers, which were expected to easily phase separate into POSS-rich and POSS-free polynorbornenyl phases, in order to investigate their morphology.

## EXPERIMENTAL DETAILS

**Polymerizations.** The polymers were all synthesized under nitrogen using the ROMP catalyst (Strem Chemicals),  $\text{Mo}(=\text{CHCMe}_2\text{Ph})(2,6\text{-di}^i\text{PrC}_5\text{H}_3\text{N})(\text{OC}_4\text{H}_9)_2$ , in anhydrous chloroform with various proportions of norbornene and either of the two POSS-norbornenyl derivatives **1a** and **1b** (see Figure 1). The reactions were designed to yield polymers with degrees of polymerization of 500 by controlling the ratio of monomers to catalyst. The reactions were terminated by addition of benzaldehyde. To generate random copolymers, the POSS-norbornenes and norbornene were dissolved together in chloroform prior to addition of the catalyst. To synthesize diblock copolymers (see Figure 1), the catalyst was added to a chloroform solution of the POSS-norbornene and, after allowing 30 minutes for polymerization, a solution of norbornene was added to the already polymerized POSS-norbornene. The polymers were precipitated and purified by adding the chloroform solution to a large excess of methanol and collecting the precipitate. This resulted in copolymers isolated in yields over 90 %.

**Thermal analysis.** The glass transition temperatures were determined using a TA Instruments differential scanning calorimeter (DSC). The temperature corresponding to the midpoint in the heat capacity step-rise is used for this purpose. The second heating run data are used with samples heated at a rate of 10 °C/min (See Figures 2 and 3).


**Transmission electron microscopy.** TEM micrographs (See Figure 4) were obtained from ultramicrotomed thin sections of films of 0, 10, 30 and 60 wt % POSS-norbornene copolymers cast from para-xylene. Bright field images were obtained using combined mass-thickness and phase contrast with a 120 keV JEOL 1200EX TEM. Due to the high electron density difference between polynorbornene and POSS molecules enough contrast could be obtained without any chemical treatment. Polymer phases rich in POSS appear as dark domains, while the TEM image of polynorbornene containing no POSS is featureless.

## RESULTS


**Polymerization of POSS macromers.** Random copolymers of norbornene and either of the two POSS macromers **1a-1b** were prepared by adding a molybdenum catalyst to a well-stirred

solution of norbornene and POSS-norbornene. The molybdenum catalyzes a living ring opening metathesis polymerization; the polymerizations were designed to yield polymers with a degree of polymerization of 500. These polymers may be viewed as organic polymers randomly filled with monodisperse inorganic particulate which are covalently bound to the polymer backbone. The synthesis of diblock copolymers containing blocks of polynorbornene and polyPOSS-norbornene (See Figure 1) was achieved by first polymerizing the POSS-norbornene monomers, then adding norbornene to the living polymerization reaction. Addition of benzaldehyde clips the molybdenum catalyst from the end of each polymer and terminates the polymer chains with a =CHPh group.


**Differential scanning calorimetric characterization.** DSC measurements were taken on both the random and the diblock copolymers (See Figures 2 and 3). As expected, the random copolymers show an increase in T<sub>g</sub> as the weight % of POSS is increased. The effect on T<sub>g</sub> is larger for the cyclohexylPOSS copolymers than for their cyclopentyl analogs. The diblock copolymers only exhibit one T<sub>g</sub> for the POSS-free block, as the block of polyPOSS-norbornene has a T<sub>g</sub> well above the decomposition of the polymer.

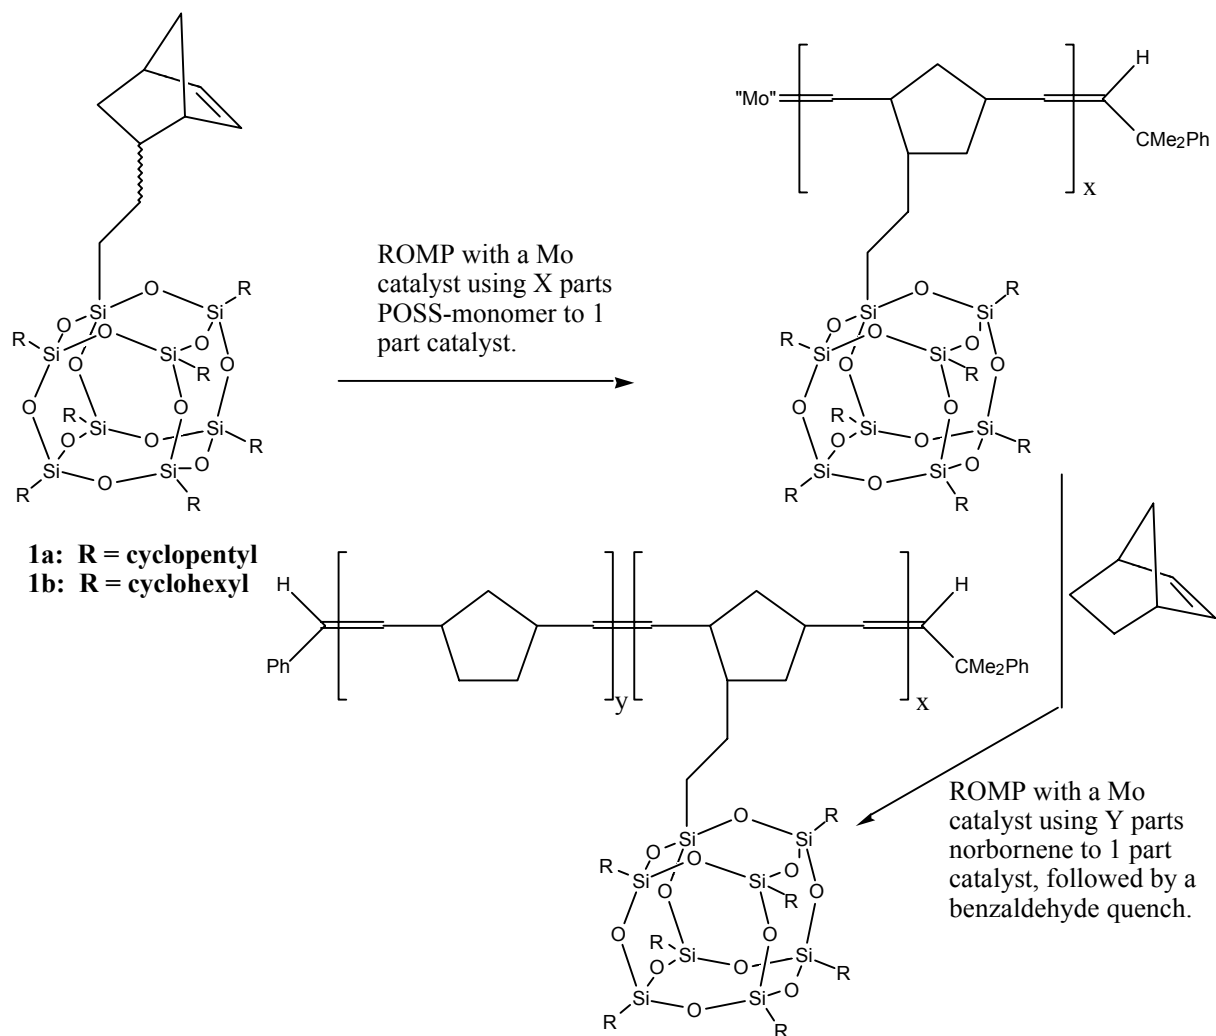


**Figure 1.** Synthesis of POSS-norbornene diblock copolymers.

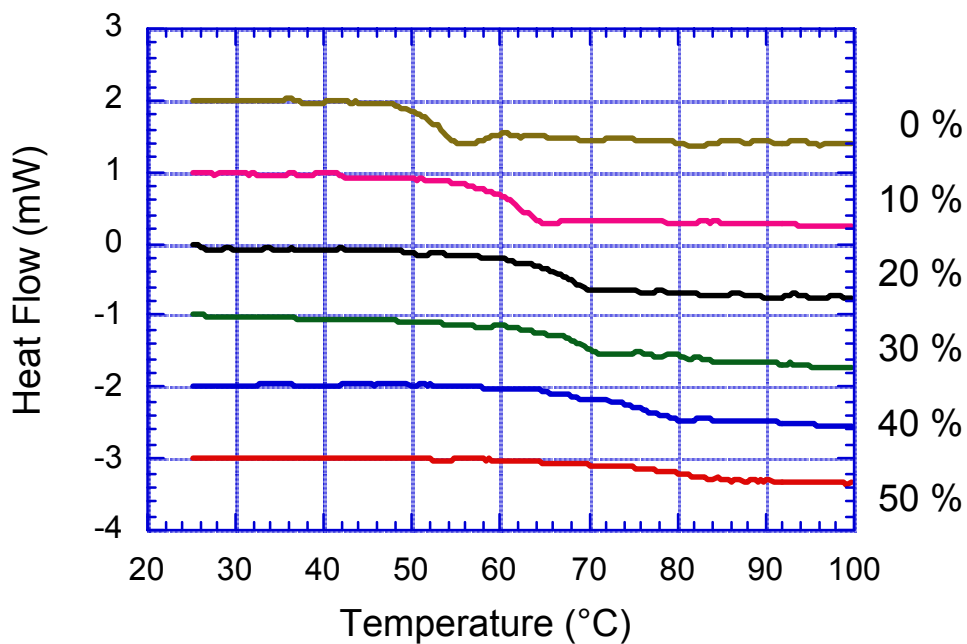

**Figure 2.** DSC traces for a series of random copolymers made from monomers of norbornene and cyclohexylPOSS-norbornene (0 to 50 weight %). A single Tg that increases with POSS content is observed.

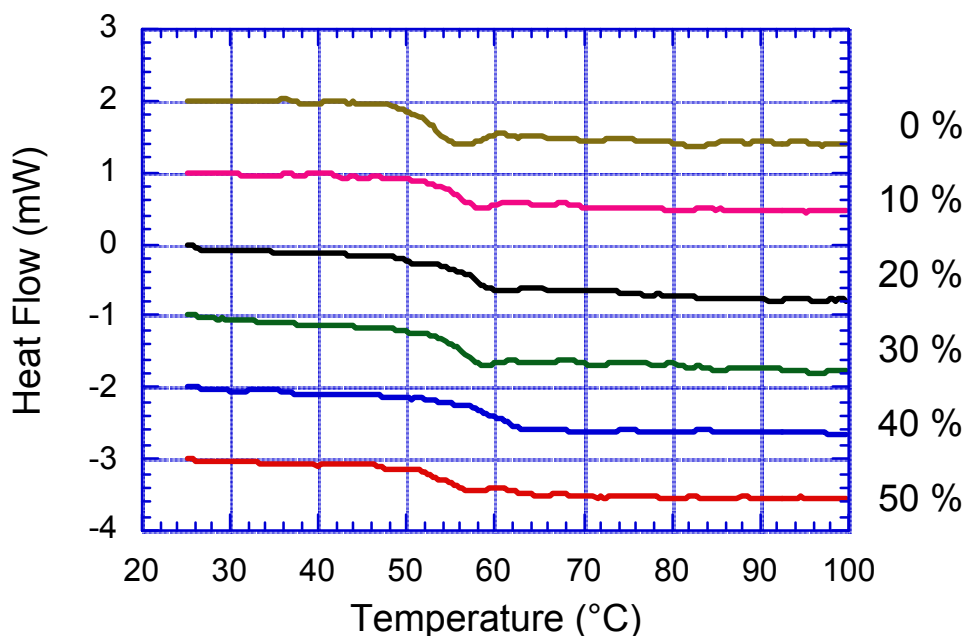

**Figure 3.** DSC traces for the series of diblock copolymers made by sequentially polymerizing monomers of norbornene and cyclohexylPOSS-norbornene (0 to 50 weight %). Only the Tg for the POSS-free polynorbornene block is observed.

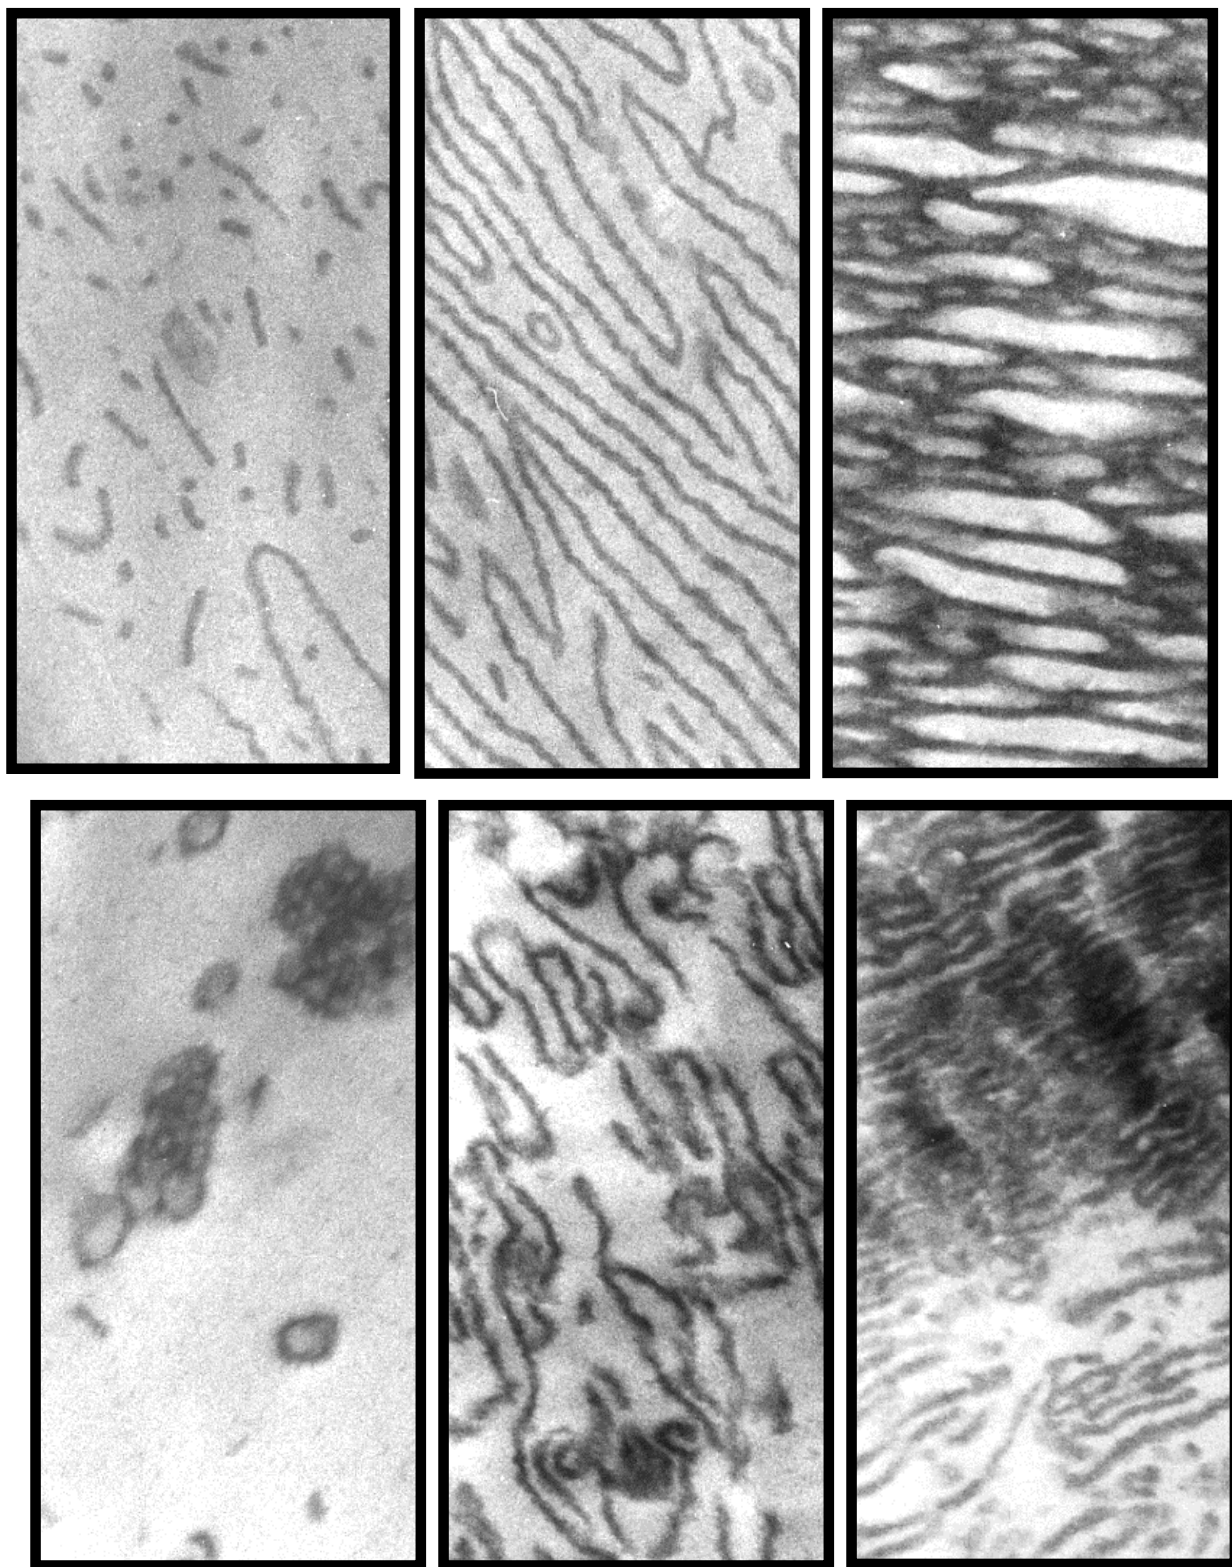

**Figure 4.** TEM images for the series of diblock copolymers made by sequentially polymerizing monomers of POSS-norbornene and norbornene. From left to right are images of polymers with 10, 30 and 60 wt % POSS. The top three images are for cyclohexylPOSS derivatives, the analogous cyclopentylPOSS pictures appear below (Each image is 1.38 microns in width).

**Transmission electron spectroscopy.** The TEM pictures of the diblock copolymers (See Figure 4) clearly image the POSS-rich domains as dark regions while the POSS-free domains are light. The TEM image of pure polynorbornene with no POSS is featureless. All images are in contrast with those of the *random* copolymers where POSS segregation was on a much shorter length scale. The random copolymers showed cylindrical POSS domains in the 63 X 12 nm size for 50 weight % cyclohexyl derivatives and 36 X 6 nm size for their cyclopentyl analogs [8]. The diblock copolymers with more than 10 weight % POSS show strong ordering into cylinders of POSS-rich blocks and clear differences are seen between the cyclopentyl and cyclohexyl-POSS analogs. The periodicity of the ordered microphases is poor and the POSS microdomain sizes are all about 28 nm except the 60 weight % cyclohexyl derivative which is about 36 nm.

## CONCLUDING REMARKS

We have demonstrated a simple method of producing both random copolymers and diblock copolymers containing inorganic nano-scale POSS groups. DSC results confirm the synthesis method. TEM images show dramatic differences between analogous polymers that differ only in the type of POSS-cage they contain. Further work will elucidate the effect of the POSS cage as new POSS monomers are investigated. For example POSS cages with isobutyl groups, and lower symmetry POSS cages with seven or nine silicons are all now available.

## ACKNOWLEDGMENTS

This research was supported by the Air Force Office of Scientific Research, Directorate of Chemistry and Life Sciences, the Air Force Research Laboratory, Propulsion Directorate, and the SERDP Office.

## REFERENCES

1. Reviews on recent progress in hybrid materials are: (a) Hybrid Organic-Inorganic Composites, *ACS Symposium Series*, ed. J. E. Mark, C. Y-C. Lee and P. A. Bianconi, **Vol. 585** (1995). (b) Better Ceramics Through Chemistry VII: Organic/Inorganic Hybrid Materials, *MRS Symposium Proceedings*, ed. B. K. Coltrain, C. Sanchez, D. W. Schaefer and G. L. Wilkes, **Vol. 435** (1996). (c) Organic/Inorganic Hybrid Materials, *MRS Symposium Proceedings*, ed. R. M. Laine, C. Sanchez, C. J. Brinker, E. Giannelis, **Vol. 519** (1998). (d) Organic/Inorganic Hybrid Materials II, *MRS Symposium Proceedings*, ed. L. C. Klein, L. F. Francis, M. R. De Guire, J. E. Mark, **Vol. 576** (1999).
2. (a) J. D. Lichtenhan, N. Q. Vu, J. A. Carter, J. W. Gilman and F. J. Feher, *Macromolecules*, **26**, 2141 (1993). (b) J. D. Lichtenhan, Y. A. Otonari and M. J. Carr, *Macromolecules*, **28**, 8435 (1995). (c) R. Mantz, P. F. Jones, K. P. Chaffee, J. D. Lichtenhan, J. W. Gilman, I. Ismail and M. J. Burmeister, *Chem. Mater.*, **8**, 1259 (1996). (d) T. S. Haddad and J. D.

- Lichtenhan, *Macromolecules*, **29**, 7302 (1996). (e) A. Romo-Uribe, P. T. Mather, T. S. Haddad, and J. D. Lichtenhan, *J. Polym. Sci. Part B: Polym. Phys.*, **36**, 1857 (1998). (f) P.T. Mather, H. G. Jeon, A. Romo-Uribe, T. S. Haddad and J. D. Lichtenhan, *Macromolecules*, **32**, 1194 (1999).
3. A. Tsuchida, C. Bolln, F. G. Sernetz, H. Frey and R. Mulhaupt, *Macromolecules*, **30**, 2818 (1997).
  4. J. Pyun and K. Matyjaszewski, *Macromolecules*, **33**, 2818 (2000).
  5. R. K. Bharadwaj, R. J. Berry and B. L. Farmer, *Polymer Preprints*, **41(1)**, 530 (2000).
  6. F. Gao, B. M. Culbertson, Y. Tong and S. R. Schricker, *Polymer Preprints*, **41(1)**, 580 (2000).
  7. B. X. Fu, W. Zhang, B. S. Hsiao, G. Johansson, B. B. Sauer, S. Phillips, R. Blanski, M. Rafailovich and J. Sokolov, *Polymer Preprints*, **41(1)**, 587 (2000).
  8. H. J. Jeon, P. T. Mather and T. S. Haddad, *Polymer International*, (2000) (in press).